


**UNITED NATIONS / DOT
PERFORMANCE CERTIFICATION**



4G PERIODIC RETEST

**6 x 2.6 Liter Plastic Bottle Packaging (4)
Variables**

TEST REPORT #: 24-CA20064 (REV 1)

 4G / Y30.6 / S / **
USA / +CC7198

**Insert the year packaging is manufactured

TESTING PERFORMED FOR:

PUREPAK TECHNOLOGY CORPORATION
75 West Baseline Road Suite D44
Gilbert, AZ 85233

ATTN: Michael Dodd

TESTING PERFORMED BY:

TEN-E PACKAGING SERVICES, INC.
326 North Corona Avenue
Ontario, CA 91764
Phone: 909-937-1260
Fax: 909-937-1262

Issue Date: May 2, 2024
Revision Date: October 22, 2024

TABLE OF CONTENTS

SECTION I: CERTIFICATION 3
SECTIONS II & V: PACKAGING DESCRIPTIONS / COMPONENT DRAWINGS 4
 COMPONENT INFORMATION 6
SECTION III: TEST PROCEDURES AND RESULTS 9
 DROP TESTS Design #1 9
 DROP TESTS Design #2 10
 DROP TESTS Design #3 11
 DROP TESTS Design #4 12
 STACKING TEST Designs #1 & #3 13
 STACKING TEST Designs #2 & #4 14
 PRESSURE DIFFERENTIAL TEST 38mm Closure 15
 PRESSURE DIFFERENTIAL TEST 45mm Closure 16
 VIBRATION TEST Design #1 17
 VIBRATION TEST Design #2 18
 VIBRATION TEST Design #3 19
 VIBRATION TEST Design #4 20
 COBB WATER ABSORPTION TEST 21
REGULATORY AND INDUSTRY STANDARD REFERENCES 22
SECTION IV: MATHEMATICAL CALCULATIONS 23
ULATIODesigns #3 & #4 25

REVISION HISTORY

Note for Rev 1: Report 24-CA20064 issued on May 2, 2024, has been updated as of October 22, 2024, updating the drop test photo orientations on pages 9 - 12.

NOTES AND COMMENTS

6 x 2.6 Liter Plastic Bottle Packaging (4) Variables

- #1) 38-439 Closure & Shipper Taped Top and Bottom Flaps
- #2) 38-439 Closure & Shipper Taped Top and Hot Melt Glued Bottom Flaps
- #3) 45mm Closure & Shipper Taped Top and Bottom Flaps
- #4) 45mm Closure & Shipper Taped Top and Hot Melt Glued Bottom Flaps

PurePak Technology may use Identification +CC7198 for alternative plastic bottle designs provided they meet the requirements of 49 CFR; 178.601 (g)(1) Selective Testing Variation 1 and 49 CFR; 178.601 (g)(4) Selective Testing Variation 4.


SECTION I: CERTIFICATION

**Periodic Retest of the PurePak Technology Corporation
 6 x 2.6 Liter Plastic Bottle Packaging (4) Variables**

TEN-E Packaging Services, Inc. is a current DOT UN Third-Party Certification Agency under §107.403 and certifies that the **PurePak Technology Corporation** packaging referenced above has passed the standards of the DEPARTMENT OF TRANSPORTATION'S TITLE 49 CFR; Performance Oriented Packaging Standards, Section 178. This package is also certified under IMDG, ICAO/IATA Regulations and the UN Recommendations on the Transport of Dangerous Goods. It is the responsibility of the end user to determine authorization for use under these regulations. The use of other packaging methods or components other than those documented in this report may render this certification invalid.

SUMMARY OF PERFORMANCE TESTS

UN / DOT TEST	49 CFR REFERENCE	TEST LEVEL	TEST CONTENTS	TEST COMPLETED	TEST RESULTS
Drop	178.603	1.9 m	Methanol/Water Solution	May 1, 2024	PASS
Stacking (#1 & #3)	178.606	272.1 Kg – 24 Hours	Empty	April 26, 2024	PASS
Stacking (#2 & #4)	178.606	272.1 Kg – 24 Hours	Empty	April 30, 2024	PASS
Pressure	173.27	300 kPa - 30 Minutes	Water	May 2, 2024	PASS
Vibration	178.608	3.4 Hz – 1 Hour	Water	April 24, 2024	PASS
Cobb	178.516	30 Minutes	---	April 2, 2024	PASS

TEST REPORT NUMBERS:	24-CA20064, 22-CA20077
UN MARKING: (CFR 49 – 178.503)	 4G / Y30.6 / S / ** USA / +CC7198
PACKAGING IDENTIFICATION CODE:	4G - Fiberboard Box (178.516)
PERFORMANCE STANDARD:	Y (Packaging meets Packing Group II and III tests)
AUTHORIZED GROSS MASS:	30.6 Kg (67.4 Lbs.)
"S" DESIGNATION:	Denotes Inner Packagings
YEAR OF MANUFACTURE:	** Insert year the packaging is manufactured
STATE AUTHORIZING THE MARK:	USA
PACKAGING CERTIFICATION AGENCY:	(+CC) TEN-E Packaging Services, Inc. (Ontario, CA CAA #2006030021)
THIRD PARTY PACKAGING IDENTIFICATION:	+CC7198
PERIODIC RETEST DATE:	May 2, 2026
SP NUMBER:	DOT-SP 14656

ALL OTHER WARRANTIES, EXPRESSED OR IMPLIED, INCLUDING ANY WARRANTY THAT THE PACKAGING TESTED IS MERCHANTABLE OR FIT FOR A PARTICULAR PURPOSE, ARE DISCLAIMED. In no event shall TEN-E Packaging Services, Inc. liability exceed the total amount paid by **PurePak Technology Corporation** for services rendered. In the event of future changes to the above referenced test standards, it is the responsibility of **PurePak Technology Corporation** to determine whether additional testing or updating of past testing is necessary to verify that the packaging we have tested remains in compliance with those standards.

MANUFACTURER:

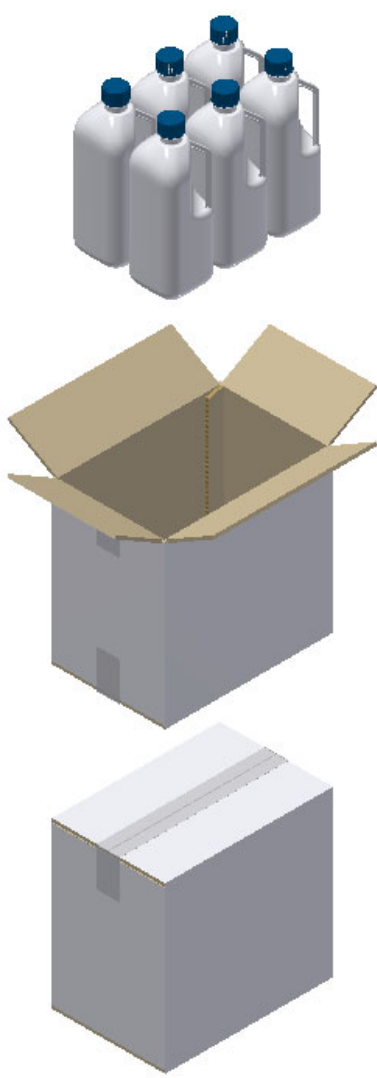
PurePak Technology Corporation
 75 West Baseline Road Suite D44
 Gilbert, AZ 85233



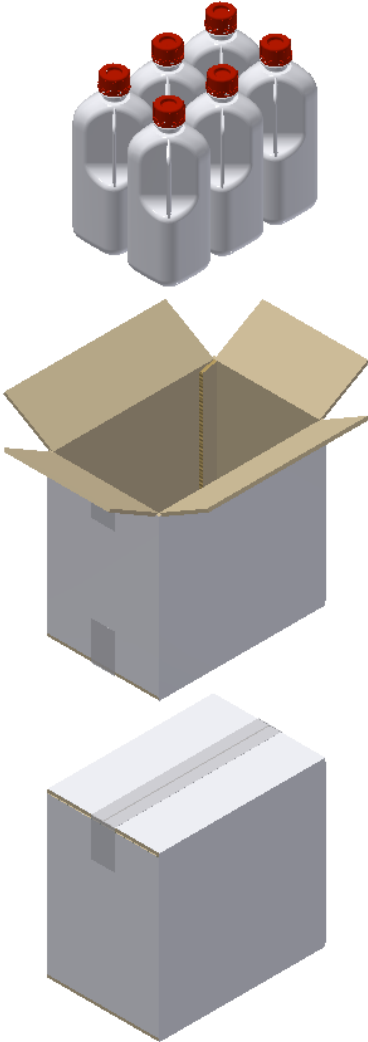
Matthew C. Anderson
 Project Manager
 TEN-E Packaging Services, Inc.
 326 North Corona Avenue
 Ontario, CA 91764

SECTIONS II & V: PACKAGING DESCRIPTIONS / COMPONENT DRAWINGS

6 x 2.6 Liter Plastic Bottles with 38-439 Closure Packaging with Two Case Sealing Mechanisms

ASSEMBLY DRAWING	TEST LEVELS			
	<table border="0"> <tr> <td>Certification Type:</td> <td>Periodic Retest</td> </tr> </table>	Certification Type:	Periodic Retest	
	Certification Type:	Periodic Retest		
	<table border="0"> <tr> <td>Packaging Code Designation:</td> <td>4G</td> </tr> </table>	Packaging Code Designation:	4G	
	Packaging Code Designation:	4G		
	<table border="0"> <tr> <td>Packing Group:</td> <td>II</td> </tr> </table>	Packing Group:	II	
	Packing Group:	II		
	<table border="0"> <tr> <td>Specific Gravity:</td> <td>1.9</td> </tr> </table>	Specific Gravity:	1.9	
	Specific Gravity:	1.9		
	<table border="0"> <tr> <td>Internal Pressure:</td> <td>300 kPa</td> </tr> </table>	Internal Pressure:	300 kPa	
	Internal Pressure:	300 kPa		
	<p align="center">TEST SAMPLE PREPARATION (Refer to Section IV)</p>			
	<table border="0"> <tr> <td>Overall Packaging Tare Weight:</td> <td>1,867.0 Grams</td> </tr> </table>		Overall Packaging Tare Weight:	1,867.0 Grams
	Overall Packaging Tare Weight:	1,867.0 Grams		
	<table border="0"> <tr> <td>Fill Capacity (98% Maximum Capacity):</td> <td></td> </tr> </table>		Fill Capacity (98% Maximum Capacity):	
	Fill Capacity (98% Maximum Capacity):			
<table border="0"> <tr> <td> Methanol/Water Solution</td> <td>2,399.0 Grams</td> </tr> </table>		Methanol/Water Solution	2,399.0 Grams	
Methanol/Water Solution	2,399.0 Grams			
<table border="0"> <tr> <td> Water</td> <td>2,520.6 Grams</td> </tr> </table>		Water	2,520.6 Grams	
Water	2,520.6 Grams			
<table border="0"> <tr> <td>Package Test Weight:</td> <td></td> </tr> </table>		Package Test Weight:		
Package Test Weight:				
<table border="0"> <tr> <td> Methanol/Water Solution</td> <td>16.2 Kg</td> <td>35.7 Lbs.</td> </tr> </table>		Methanol/Water Solution	16.2 Kg	35.7 Lbs.
Methanol/Water Solution	16.2 Kg	35.7 Lbs.		
<table border="0"> <tr> <td> Water</td> <td>16.9 Kg</td> <td>37.2 Lbs.</td> </tr> </table>		Water	16.9 Kg	37.2 Lbs.
Water	16.9 Kg	37.2 Lbs.		
<table border="0"> <tr> <td>Authorized Package Gross Mass:</td> <td>30.6 Kg</td> <td>67.4 Lbs.</td> </tr> </table>		Authorized Package Gross Mass:	30.6 Kg	67.4 Lbs.
Authorized Package Gross Mass:	30.6 Kg	67.4 Lbs.		
<p align="center">CLOSING METHODS – INNER PACKAGING</p>				
<table border="0"> <tr> <td>Application Torque:</td> <td>50 In-Lbs.</td> </tr> </table>		Application Torque:	50 In-Lbs.	
Application Torque:	50 In-Lbs.			
<table border="0"> <tr> <td>Equipment:</td> <td>Snap On Torque Wrench</td> </tr> </table>		Equipment:	Snap On Torque Wrench	
Equipment:	Snap On Torque Wrench			
<p align="center">CLOSING METHODS – SHIPPER</p>				
<p align="center">Top Flaps:</p>				
<table border="0"> <tr> <td>Manufacturer:</td> <td>3M, St. Paul, MN</td> </tr> </table>		Manufacturer:	3M, St. Paul, MN	
Manufacturer:	3M, St. Paul, MN			
<table border="0"> <tr> <td>Type:</td> <td>3M Part Number MMM115994 Pressure Sensitive Tape</td> </tr> </table>		Type:	3M Part Number MMM115994 Pressure Sensitive Tape	
Type:	3M Part Number MMM115994 Pressure Sensitive Tape			
<table border="0"> <tr> <td>Width:</td> <td>48 mm (2")</td> </tr> </table>		Width:	48 mm (2")	
Width:	48 mm (2")			
<table border="0"> <tr> <td>Overlap:</td> <td>2" Minimum</td> </tr> </table>		Overlap:	2" Minimum	
Overlap:	2" Minimum			
<table border="0"> <tr> <td>Tape Pattern:</td> <td>Center Seam</td> </tr> </table>		Tape Pattern:	Center Seam	
Tape Pattern:	Center Seam			
<p align="center">Bottom Flaps:</p>				
<table border="0"> <tr> <td>Manufacturer:</td> <td>3M, St. Paul, MN</td> </tr> </table>		Manufacturer:	3M, St. Paul, MN	
Manufacturer:	3M, St. Paul, MN			
<table border="0"> <tr> <td>Type:</td> <td>Option #1) 3M Part Number MMM115994 Pressure Sensitive Tape</td> </tr> </table>		Type:	Option #1) 3M Part Number MMM115994 Pressure Sensitive Tape	
Type:	Option #1) 3M Part Number MMM115994 Pressure Sensitive Tape			
<table border="0"> <tr> <td>Type:</td> <td>Option #2) Hot Melt Glue (6 Parallel ¼" x 3" Strips Per Bottom Inner Flap – Prepared by Client)</td> </tr> </table>		Type:	Option #2) Hot Melt Glue (6 Parallel ¼" x 3" Strips Per Bottom Inner Flap – Prepared by Client)	
Type:	Option #2) Hot Melt Glue (6 Parallel ¼" x 3" Strips Per Bottom Inner Flap – Prepared by Client)			
<table border="0"> <tr> <td>Width:</td> <td>48 mm (2")</td> </tr> </table>		Width:	48 mm (2")	
Width:	48 mm (2")			
<table border="0"> <tr> <td>Overlap:</td> <td>2" Minimum</td> </tr> </table>		Overlap:	2" Minimum	
Overlap:	2" Minimum			
<table border="0"> <tr> <td>Tape Pattern:</td> <td>Center Seam</td> </tr> </table>		Tape Pattern:	Center Seam	
Tape Pattern:	Center Seam			

6 x 2.6 Liter Plastic Bottles with 45mm Closure Packaging with Two Case Sealing Mechanisms

ASSEMBLY DRAWING	TEST LEVELS		
	Certification Type:	Periodic Retest	
	Packaging Code Designation:	4G	
	Packing Group:	II	
	Specific Gravity:	1.9	
	Internal Pressure:	300 kPa	
	TEST SAMPLE PREPARATION (Refer to Section IV)		
	Overall Packaging Tare Weight:	1,875.0 Grams	
	Fill Capacity (98% Maximum Capacity):		
	Methanol/Water Solution	2,380.5 Grams	
	Water	2,522.6 Grams	
	Package Test Weight:		
	Methanol/Water Solution	16.1 Kg	35.4 Lbs.
	Water	17.0 Kg	37.4 Lbs.
	Authorized Package Gross Mass:	30.6 Kg	67.4 Lbs.
	CLOSING METHODS – INNER PACKAGING		
Application Torque:	25 In-Lbs.		
Equipment:	Snap On Torque Wrench		
CLOSING METHODS – SHIPPER			
Top Flaps:			
Manufacturer:	3M, St. Paul, MN		
Type:	3M Part Number MMM115994 Pressure Sensitive Tape		
Width:	48 mm (2")		
Overlap:	2" Minimum		
Tape Pattern:	Center Seam		
Bottom Flaps:			
Manufacturer:	3M, St. Paul, MN		
Type:	Option #1) 3M Part Number MMM115994 Pressure Sensitive Tape Option #2) Hot Melt Glue (6 Parallel ¼" x 3" Strips Per Bottom Inner Flap – Prepared by Client)		
Width:	48 mm (2")		
Overlap:	2" Minimum		
Tape Pattern:	Center Seam		

COMPONENT INFORMATION

CLOSURE (500093)		DRAWING
Manufacturer: Berry Plastics, Evansville, IN		
Description:	38mm Threaded Closure	
Quantity:	6	
Material:	Polypropylene	
Tare Weight:	10.63 Grams	
Overall Dimensions:		
• Height	1.019" ± 0.015"	
• Diameter	1.703" ± 0.015"	
Thread:		
• Type	38mm	
• Style	439	
Finish Dimensions:		
• T	1.480" ± 0.007"	
• E	1.389" ± 0.007"	
Markings (QC Audit):	1	
LINER:		
Description:	Polyethylene Foam Liner	
Tare Weight:	0.67 Grams	
Thickness:	0.059"	
Diameter:	1.397"	
PLASTIC BOTTLE (1221443)		
Manufacturer: PurePak Technology, Gilbert, AZ		
Description:	2.6 Liter Plastic Bottle with 38mm Threads	
Quantity:	6	
Material:	High Density Polyethylene	
Method of Manufacture:	Blow Molded	
Tare Weight:	208.0 Grams	
Capacity:		
• Rated	2.6 Liter	
• Overflow	2,572.0 Grams	
Overall Dimensions:		
• Height	12.120" ± 0.080"	
• Width	5.302" ± 0.080"	
• Depth	5.302" ± 0.080"	
Thread Dimensions:		
• T	1.461" ± 0.0812"	
• E	1.357" ± 0.080"	
• Pitch	0.1636"	
Wall Thickness:		
• Minimum	0.040"	
Markings (QC Audit):	SPI "2" HDPE Recycling Symbol M4609 A020724 12:15 / 7000 MADE IN USA 2/24 DODD 1	

CLOSURE (500001)		DRAWING
Manufacturer: George MENSHEN GmbH, Finnentrop, Germany		
Description:	45mm Threaded Closure Tamper Evident	
Quantity:	6	
Material:	High Density Polyethylene	
Tare Weight:	10.64 Grams	
Overall Dimensions:		
• Height	30.3mm	
• Diameter	1.992"	
Thread:		
• Type	45mm	
• Style	Buttress	
Finish Dimensions:		
• T	1.766"	
• E	1.682"	
• Pitch	4mm	
Markings (QC Audit):	2817.1 4	
LINER:		
Description:	PTFE Liner	
Tare Weight:	Grams	
Thickness:	0.010"	
Diameter:	1.767"	
PLASTIC BOTTLE (1927106)		
Manufacturer: PurePak Technology, Gilbert, AZ		
Description:	2.6 Liter Plastic Bottle with 45mm Threads	
Quantity:	6	
Material/Pigment:	High Density Polyethylene / Natural	
Method of Manufacture:	Blow Molded	
Tare Weight:	208.0 Grams	
Capacity:		
• Rated	2.6 Liter	
• Overflow	2,574.0 Grams	
Overall Dimensions:		
• Height	12.120" ± 0.090"	
• Width	5.270" ± 0.080"	
• Depth	5.270" ± 0.080"	
Thread Dimensions:		
• T	1.772" ± 0.010"	
• E	1.644" ± 0.010"	
• Pitch	1.540"	
Wall Thickness:		
• Minimum	0.038"	
Markings (QC Audit):	SPI "2" HDPE Recycling Symbol M4609 A020724 12:15 / 7000 MADE IN USA 2/24 DODD 1	



TEN-E Packaging Services, Inc.

Test Report # 24-CA20064 (Rev 1)

Issue Date: May 2, 2024

Revision Date: October 22, 2024

Page 8 of 26

SHIPPER (Part # 731195 & 1394833)

Manufacturer: PCA, Phoenix, AZ

Description: Regular Slotted Container

Material/Flute (Inner to Outer): Double Wall Mottled White Corrugated Fiberboard; C/B-Flute

Basis Weight (Outer to Inner) Lbs./MSF:

• **Specification** 35 / 23 / 35 / 23 / 35

Tare Weight: 548.0 Grams

DIMENSIONS


	Specification Dimensions (Inside)	Measured Dimensions (Outside)
--	-----------------------------------	-------------------------------

• Length	13-3/4"	14-3/8"
• Width	9"	9-5/8"
• Height	12-3/8"	13-1/2"

Board Caliper (Nominal): 0.253"

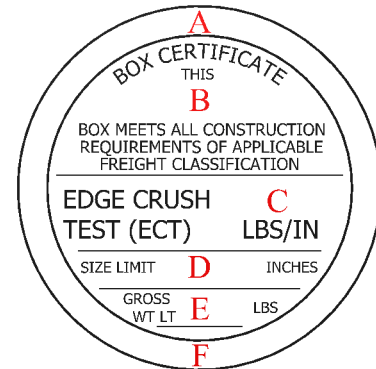
Manufacturer's Joint: Inside Glued, 1-3/8" Lap

Markings (QC Audit):

 4G/Y30.6/S/23 DOT-SP 14656
 USA/+CC7198
 ART WORK DATE 08/28/23 13.75 X 9 X 12.375 ID 1394833 DOT-SP 14656
 121175

BOX CERTIFICATE

(A) Corrugated Manufacturer:	-----
(B) Structure:	Double Wall
(C) ECT:	51 Lbs. Per Sq. Inch
(D) Size Limit:	105"
(E) Gross Wt. Lt:	120 Lbs.
(F) Location:	-----






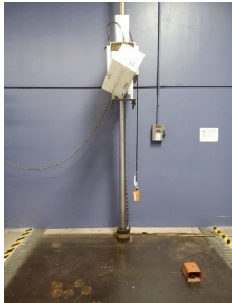


SECTION III: TEST PROCEDURES AND RESULTS

DROP TESTS Design #1

TEST INFORMATION		TEST CRITERIA
TEST CONTENTS:	Methanol/Water Solution (0.965 SG)	<ul style="list-style-type: none"> For packaging containing liquid, each packaging does not leak. There can be no damage to the outer packaging likely to adversely affect safety during transport. Inner receptacles, inner packagings or articles must remain completely within the outer packaging and there must be no leakage of the filling substance from the inner packaging. Any discharge from a closure is slight and ceases immediately after impact with no further leakage. (\$178.603)
SAMPLE PREPARATION:	Refer to Section II	
CONDITIONING:	-18°C (0°F) Freezer #W201	
CONTENTS TEMP.:	-18.4°C (-1.1°F)	
DROP HEIGHT:	1.9 Meters (75.0") (Refer to Section IV)	
TEST EQUIPMENT:	L.A.B. Accu Drop 160	

DROP ORIENTATIONS AND TEST RESULTS

Sample #1: Flat on Bottom	Sample #2: Flat on Top	*Sample #3: Flat on Long Side
		
PASS: No leakage or damage.	PASS: No leakage or damage.	PASS: No leakage or damage.
*Sample #4: Flat on Short Side	*Sample #5: Bottom Corner	**Sample #1: Top Corner
		
PASS: No leakage or damage.	PASS: No leakage. Slight deformation at impact corner.	PASS: No leakage. Slight deformation at impact corner.






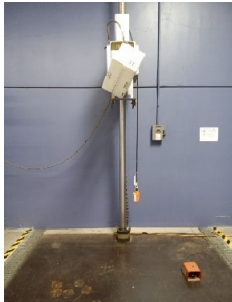
*Side and corner drops were conducted to impact the manufacturer's joint.

**Flat on bottom drop sample was also used for the top corner drop.

DROP TESTS Design #2

TEST INFORMATION		TEST CRITERIA
TEST CONTENTS:	Methanol/Water Solution (0.965 SG)	<ul style="list-style-type: none"> For packaging containing liquid, each packaging does not leak. There can be no damage to the outer packaging likely to adversely affect safety during transport. Inner receptacles, inner packagings or articles must remain completely within the outer packaging and there must be no leakage of the filling substance from the inner packaging. Any discharge from a closure is slight and ceases immediately after impact with no further leakage. (§178.603)
SAMPLE PREPARATION:	Refer to Section II	
CONDITIONING:	-18°C (0°F) Freezer #W201	
CONTENTS TEMP.:	-18.4°C (-1.1°F)	
DROP HEIGHT:	1.9 Meters (75.0") (Refer to Section IV)	
TEST EQUIPMENT:	L.A.B. Accu Drop 160	

DROP ORIENTATIONS AND TEST RESULTS

Sample #12: Flat on Bottom	Sample #13: Flat on Top	*Sample #14: Flat on Long Side
		
PASS: No leakage or damage.	PASS: No leakage or damage.	PASS: No leakage or damage.
*Sample #15: Flat on Short Side	*Sample #16: Bottom Corner	**Sample #12: Top Corner
		
PASS: No leakage or damage.	PASS: No leakage. Slight deformation at impact corner.	PASS: No leakage. Slight deformation at impact corner.

*Side and corner drops were conducted to impact the manufacturer's joint.

**Flat on bottom drop sample was also used for the top corner drop.

DROP TESTS

Design #3

TEST INFORMATION		TEST CRITERIA
TEST CONTENTS:	Methanol/Water Solution (0.965 SG)	<ul style="list-style-type: none"> For packaging containing liquid, each packaging does not leak. There can be no damage to the outer packaging likely to adversely affect safety during transport. Inner receptacles, inner packagings or articles must remain completely within the outer packaging and there must be no leakage of the filling substance from the inner packaging. Any discharge from a closure is slight and ceases immediately after impact with no further leakage. (§178.603)
SAMPLE PREPARATION:	Refer to Section II	
CONDITIONING:	-18°C (0°F) Freezer #W201	
CONTENTS TEMP.:	-18.4°C (-1.1°F)	
DROP HEIGHT:	1.9 Meters (75.0") (Refer to Section IV)	
TEST EQUIPMENT:	L.A.B. Accu Drop 160	

DROP ORIENTATIONS AND TEST RESULTS

Sample #23: Flat on Bottom	Sample #24: Flat on Top	*Sample #25: Flat on Long Side
PASS: No leakage or damage.	PASS: No leakage or damage.	PASS: No leakage or damage.
*Sample #26: Flat on Short Side	*Sample #27: Bottom Corner	**Sample #23: Top Corner
PASS: No leakage or damage.	PASS: No leakage. Slight deformation at impact corner.	PASS: No leakage. Slight deformation at impact corner.

*Side and corner drops were conducted to impact the manufacturer's joint.






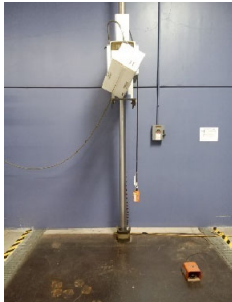
**Flat on bottom drop sample was also used for the top corner drop.

DROP TESTS

Design #4

TEST INFORMATION		TEST CRITERIA
TEST CONTENTS:	Methanol/Water Solution (0.965 SG)	<ul style="list-style-type: none"> For packaging containing liquid, each packaging does not leak. There can be no damage to the outer packaging likely to adversely affect safety during transport. Inner receptacles, inner packagings or articles must remain completely within the outer packaging and there must be no leakage of the filling substance from the inner packaging. Any discharge from a closure is slight and ceases immediately after impact with no further leakage. (§178.603)
SAMPLE PREPARATION:	Refer to Section II	
CONDITIONING:	-18°C (0°F) Freezer #W201	
CONTENTS TEMP.:	-18.4°C (-1.1°F)	
DROP HEIGHT:	1.9 Meters (75.0") (Refer to Section IV)	
TEST EQUIPMENT:	L.A.B. Accu Drop 160	

DROP ORIENTATIONS AND TEST RESULTS

Sample #31: Flat on Bottom	Sample #32: Flat on Top	*Sample #33: Flat on Long Side
		
PASS: No leakage or damage.	PASS: No leakage or damage.	PASS: No leakage or damage.
*Sample #34: Flat on Short Side	*Sample #35: Bottom Corner	**Sample #31: Top Corner
		
PASS: No leakage or damage.	PASS: No leakage. Slight deformation at impact corner.	PASS: No leakage. Slight deformation at impact corner.

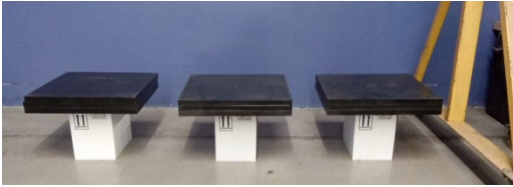
*Side and corner drops were conducted to impact the manufacturer's joint.

**Flat on bottom drop sample was also used for the top corner drop.

STACKING TEST Designs #1 & #3

TEST INFORMATION		TEST CRITERIA
TEST CONTENTS:	Empty	<ul style="list-style-type: none"> There can be no deterioration that could adversely affect transport safety or any distortion liable to reduce the package's strength, cause instability in stacks of packages, or cause damage to inner packagings that is likely to reduce safety in transport. <p style="text-align: right;">(\$178.606)</p>
SAMPLE PREPARATION:	Refer to Section II	
CONDITIONING:	Ambient	
TEST LOAD APPLIED:	272.1 Kg (600.0 Lbs.) (Refer to Section IV)	
TEST DURATION:	24 Hours	
TEST EQUIPMENT:	Dead Load Weights	

STACKING TEST SET-UP & RESULTS

	Sample #	Maximum Deflection After 24 Hours	Results
	6	1/16"	PASS
	7	1/8"	PASS
	8	1/8"	PASS

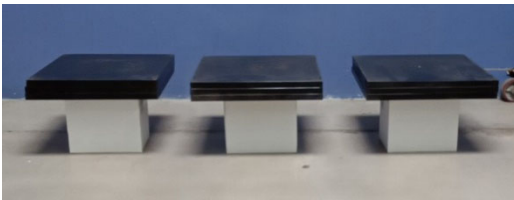
Comments/Observations: Following the 24-hour stack test, there was no damage likely to affect the performance of the packaging.

Stacking Stability: Not conducted; required only for guided load tests.

STACKING TEST Designs #2 & #4

TEST INFORMATION		TEST CRITERIA
TEST CONTENTS:	Empty	<ul style="list-style-type: none"> There can be no deterioration that could adversely affect transport safety or any distortion liable to reduce the package's strength, cause instability in stacks of packages, or cause damage to inner packagings that is likely to reduce safety in transport. <p style="text-align: right;">(\$178.606)</p>
SAMPLE PREPARATION:	Refer to Section II	
CONDITIONING:	Ambient	
TEST LOAD APPLIED:	272.1 Kg (600.0 Lbs.) (Refer to Section IV)	
TEST DURATION:	24 Hours	
TEST EQUIPMENT:	Dead Load Weights	

STACKING TEST SET-UP & RESULTS

	Sample #	Maximum Deflection After 24 Hours	Results
	17	1/16"	PASS
	18	1/16"	PASS
	19	1/16"	PASS

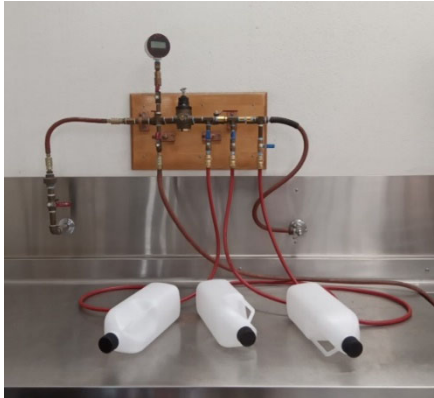

Comments/Observations: Following the 24-hour stack test, there was no damage likely to affect the performance of the packaging.

Stacking Stability: Not conducted; required only for guided load tests.

PRESSURE DIFFERENTIAL TEST 38mm Closure

TEST INFORMATION		TEST CRITERIA
TEST CONTENTS:	Water	<ul style="list-style-type: none"> • Packaging for which retention of liquid is a basic function must be capable of withstanding the pressure requirements without leakage. (§173.27(c))
WATER TEMPERATURE:	(61.4°F)	
FILL CAPACITY:	Maximum Capacity	
CLOSURE APPLICATION:	Refer to Section II	
CONDITIONING:	Ambient	
TEST PRESSURE:	300 kPa	
TEST DURATION:	30 Minutes	
AREA OF PRESSURIZATION:	Through the Bottom	
TEST EQUIPMENT:	Regulated Water Source Digital Pressure Gauge #: 605	

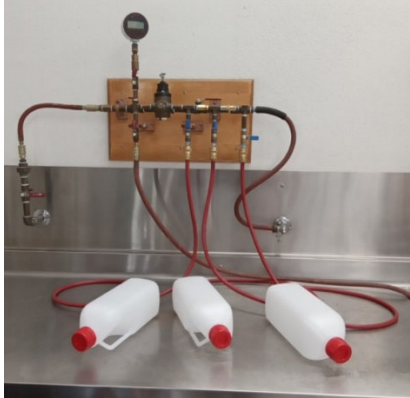

HYDROSTATIC PRESSURE TEST SET-UP AND RESULTS

		Sample #	Results
		1	PASS
		2	PASS
		3	PASS
Comments/Observations			
All three samples maintained the 300 kPa test pressure for 30 minutes without leakage.			

PRESSURE DIFFERENTIAL TEST 45mm Closure

TEST INFORMATION		TEST CRITERIA
TEST CONTENTS:	Water	<ul style="list-style-type: none"> • Packaging for which retention of liquid is a basic function must be capable of withstanding the pressure requirements without leakage. (§173.27(c))
WATER TEMPERATURE:	(61.4°F)	
FILL CAPACITY:	Maximum Capacity	
CLOSURE APPLICATION:	Refer to Section II	
CONDITIONING:	Ambient	
TEST PRESSURE:	300 kPa	
TEST DURATION:	30 Minutes	
AREA OF PRESSURIZATION:	Through the Bottom	
TEST EQUIPMENT:	Regulated Water Source Digital Pressure Gauge #: 605	


HYDROSTATIC PRESSURE TEST SET-UP AND RESULTS

		Sample #	Results
		1	PASS
		2	PASS
		3	PASS
Comments/Observations			
All three samples maintained the 300 kPa test pressure for 30 minutes without leakage.			

VIBRATION TEST Design #1

TEST INFORMATION		TEST CRITERIA
TEST CONTENTS:	Water	<ul style="list-style-type: none"> Immediately following the period of vibration, each package must be removed from the platform, turned on its side and observed for any evidence of leakage. A packaging passes the vibration test if there is no rupture or leakage from any of the packages. No test sample should show any deterioration which could adversely affect transportation safety or any distortion liable to reduce packaging strength. (§178.608)
SAMPLE PREPARATION:	Refer to Section II	
CONDITIONING:	Ambient	
TABLE DISPLACEMENT:	1"	
TEST FREQUENCY:	3.4 Hz	
TEST DURATION:	1 Hour	
TEST EQUIPMENT:	Vertical motion using L.A.B. Palletizer Vibration System	


VIBRATION TEST SET-UP AND RESULTS

	Sample #	Results	Comments/Observations
	9	PASS	No leakage or damage.
	10	PASS	
	11	PASS	

VIBRATION TEST Design #2

TEST INFORMATION		TEST CRITERIA
TEST CONTENTS:	Water	<ul style="list-style-type: none"> Immediately following the period of vibration, each package must be removed from the platform, turned on its side and observed for any evidence of leakage. A packaging passes the vibration test if there is no rupture or leakage from any of the packages. No test sample should show any deterioration which could adversely affect transportation safety or any distortion liable to reduce packaging strength. (§178.608)
SAMPLE PREPARATION:	Refer to Section II	
CONDITIONING:	Ambient	
TABLE DISPLACEMENT:	1"	
TEST FREQUENCY:	3.4 Hz	
TEST DURATION:	1 Hour	
TEST EQUIPMENT:	Vertical motion using L.A.B. Palletizer Vibration System	


VIBRATION TEST SET-UP AND RESULTS

	Sample #	Results	Comments/Observations
	20	PASS	No leakage or damage.
	21	PASS	
	22	PASS	

VIBRATION TEST Design #3

TEST INFORMATION		TEST CRITERIA
TEST CONTENTS:	Water	<ul style="list-style-type: none"> Immediately following the period of vibration, each package must be removed from the platform, turned on its side and observed for any evidence of leakage. A packaging passes the vibration test if there is no rupture or leakage from any of the packages. No test sample should show any deterioration which could adversely affect transportation safety or any distortion liable to reduce packaging strength. (§178.608)
SAMPLE PREPARATION:	Refer to Section II	
CONDITIONING:	Ambient	
TABLE DISPLACEMENT:	1"	
TEST FREQUENCY:	3.4 Hz	
TEST DURATION:	1 Hour	
TEST EQUIPMENT:	Vertical motion using L.A.B. Palletizer Vibration System	


VIBRATION TEST SET-UP AND RESULTS

	Sample #	Results	Comments/Observations
	28	PASS	No leakage or damage.
	29	PASS	
	30	PASS	

VIBRATION TEST Design #4

TEST INFORMATION		TEST CRITERIA
TEST CONTENTS:	Water	<ul style="list-style-type: none"> Immediately following the period of vibration, each package must be removed from the platform, turned on its side and observed for any evidence of leakage. A packaging passes the vibration test if there is no rupture or leakage from any of the packages. No test sample should show any deterioration which could adversely affect transportation safety or any distortion liable to reduce packaging strength. (§178.608)
SAMPLE PREPARATION:	Refer to Section II	
CONDITIONING:	Ambient	
TABLE DISPLACEMENT:	1"	
TEST FREQUENCY:	3.4 Hz	
TEST DURATION:	1 Hour	
TEST EQUIPMENT:	Vertical motion using L.A.B. Palletizer Vibration System	

VIBRATION TEST SET-UP AND RESULTS

	Sample #	Results	Comments/Observations
	36	PASS	No leakage or damage.
	37	PASS	
	38	PASS	

COBB WATER ABSORPTION TEST

TEST INFORMATION	TEST CRITERIA
NUMBER OF SAMPLES: 5 SAMPLE SIZE: 5" x 5" (Minimum) CONDITIONING: 73°F / 50% RH Quality Room #W202 WATER APPLIED: 100 mL / Sample TEST DURATION: 30 Minutes / Sample TEST EQUIPMENT: UWE Analytical Balance Gurley Cobb Water Absorption Fixtures	<ul style="list-style-type: none"> An increase in mass greater than 155 g/m² over the 30 minute duration represents an unacceptable level of water resistance. (§178.516)

COBB WATER ABSORPTION TEST RESULTS

REPRESENTATIVE SET-UP PHOTO	Sample #	Water Absorbed
	1	94.0 g/m ²
	2	104.0 g/m ²
	3	132.0 g/m ²
	4	121.0 g/m ²
	5	100.0 g/m ²
	AVERAGE:	110.2 g/m²
	RESULT	PASS

REGULATORY AND INDUSTRY STANDARD REFERENCES

REGULATORY REFERENCES

TEST	49 CFR ^①	UN ^②	IMDG ^③	ICAO ^④	IATA ^⑤
	October 2022 Edition	22 nd Edition	2022 Edition	2023-2024 Edition	64 th Edition
Drop:	178.603	6.1.5.3	6.1.5.3	6;4.3	6.3.3
Stacking:	178.606	6.1.5.6	6.1.5.6	6;4.6	6.3.6
Pressure:	173.27(c)	4.1.1.4.1	---	4;1.1.6	5.0.2.9
Vibration:	178.608	---	---	4;1.1.1 & 4;1.1.4	5.0.2.7
Cobb:	178.516(b)(1)	6.1.4.12.1	6.1.4.12.1	6;3.1.11.1	6.2.12.2

① United States Department of Transportation Code of Federal Regulations (CFR) Title 49, Transportation, Parts 100-185

② The United Nations Recommendations on the Transport of Dangerous Goods – Model Regulations (UN – Orange Book)

③ International Maritime Dangerous Goods Code (IMDG)

④ Technical Instructions for the Safe Transport of Dangerous Good by Air (ICAO)

⑤ International Air Transport Association (IATA) Dangerous Goods Regulations

INDUSTRY STANDARD REFERENCES

Drop:	ASTM ^⑥ D5276:	Standard Test Method for Drop Test of Loaded Containers by Free Fall
	ASTM ^⑥ D7790:	Standard Test Method for the Preparation of Plastic Packagings Containing Liquids for United Nations (UN) Drop Testing
	ISO ^⑦ 2248:	Packaging – Complete, Filled Transport Packages – Vertical Impact Test by Dropping
Stacking:	ASTM ^⑥ D8409:	Standard Guide for Conducting Stacking Tests on UN Packagings Using Guided or Unguided Loads
	ASTM ^⑥ D4577:	Standard Test Method for Compression Resistance of a Container Under Constant Load
	ISO ^⑦ 2234:	Packaging – Complete, Filled Transport Packages – Stacking Test using Static Load
Hydrostatic Pressure:	ASTM ^⑥ D7660:	Standard Guide for Conducting Internal Pressure Tests on United Nations (UN) Packagings
Vibration:	ASTM ^⑥ D999:	Standard Test Method for Vibration Testing of Shipping Containers
	ISO ^⑦ 2247:	Packaging – Complete, Filled Transport Packages – Vibration Test at Fixed Low Frequency
Cobb:	ISO ^⑦ 535:	Paper and Board – Determination of Water Absorption – Cobb Method

⑥ American Society for Testing and Materials (ASTM)

⑦ International Organization for Standardization (ISO)

EQUIPMENT

All inspection, measuring and test equipment that can affect product quality is calibrated and adjusted at prescribed intervals, or prior to use, and is traceable to NIST, using ANSI Z540 as an overall guide for calibration certification.

This test report shall not be reproduced, except in full and unedited, without prior written approval from TEN-E Packaging Services, Inc.



TEN-E Packaging Services, Inc.

SECTION IV: MATHEMATICAL CALCULATIONS

Designs #1 & #2

INFORMATION USED FOR CALCULATIONS		
Overall Packaging Tare Weight (PTW):	1,867.0 Grams	
Overflow Capacity (OFC):		<u>Methanol/Water</u>
Methanol/Water	2,448.0 Grams	SG: 0.965
Water	2,572.0 Grams	
Number of Inner Packagings (# IP):	6	
Packing Group	II	
Product Specific Gravity (PSG):	1.900	
Packing Group Multiplication Factor (MF):	1.00	
Overall Height of one Package (OH):	13.50 Inches	
Stack Test-# of Samples Tested Simultaneously:	1	

98% OF OVERFLOW				
Overflow Capacity (OFC) x 98%				
<u>OFC</u>	x	<u>98%</u>		
2,448.0	x	98% =	2,399.1 Grams	Methanol/Water
2,572.0	x	98% =	2,520.6 Grams	Water

PACKAGE TEST WEIGHTS					
Overall Pkg Tare Weight (PTW) + (98% Overflow Capacity (OFC) x # of Inner Pkg (# IP))					
<u>PTW</u>	+	<u>(98% OFC)</u>	x	<u># IP)</u>	
1,867.0	+	2,399.1	x	6	Methanol/Water
1,867.0	+	2,520.6	x	6	Water
Methanol/Water:		16.2	kg	35.7	lb
Water:		16.9	kg	37.2	lb

AUTHORIZED PACKAGE GROSS MASS CALCULATION (APGM)						
Overall Pkg Tare Weight (PTW) + (Product SG (PSG) x 98% Overflow (OFC) x # of Inner Pkg (# IP))						
<u>PTW</u>	+	<u>(PSG</u>	x	<u>98% OFC</u>	x	<u># IP)</u>
1,867.0	+	1.9	x	2,520.6	x	6
		30.6	kg	67.4	lb	



TEN-E Packaging Services, Inc.

DROP HEIGHT

Calculation For Product Specific Gravities Exceeding 1.2
 Product Specific Gravity (PSG) x Packing Group Multiplication Factor (MF)

<u>PSG</u>	x	<u>MF</u>		<u>Required Drop Height</u>	<u>Actual Drop Height</u>
1.9	x	1.00			
		1.90	Meter	74.8 Inches	75 Inches

Packing Group: II

STACKING TEST MINIMUM LOAD CALCULATIONS

Number of Packages in a 3m High Stack (118.2 / Overall Pkg Height (OH) -1)

118.2 / Overall Height of one Pkg (OH) - 1

<u>(118.2)</u>	/	<u>OH)</u>	-1	=	<u># 3m HS</u>
118.2	/	13.50	-1	=	7.8

Stacking Test Load Calculation (Individual Package)

Authorized Pkg Gross Mass (APGM) x # of Pkg in a 3m High Stack (# 3m HS)

<u>APGM</u>	x	<u># 3m HS</u>	
30.6	x	7.8	
		238.7 kg	526.2 lb



TEN-E Packaging Services, Inc.

Designs #3 & #4

INFORMATION USED FOR CALCULATIONS

Overall Packaging Tare Weight (PTW):	1,875.0 Grams	
Overflow Capacity (OFC):		<u>Methanol/Water</u>
Methanol/Water	2,429.0 Grams	SG: 0.965
Water	2,574.0 Grams	
Number of Inner Packagings (# IP):	6	
Packing Group	II	
Product Specific Gravity (PSG):	1.900	
Packing Group Multiplication Factor (MF):	1.00	
Overall Height of one Package (OH):	13.50 Inches	
Stack Test # of Samples Tested Simultaneously:	1	

98% OF OVERFLOW

Overflow Capacity (OFC) x 98%					
OFC	x	98%			
2,429.0	x	98% =	2,380.5 Grams	Methanol/Water	
2,574.0	x	98% =	2,522.6 Grams	Water	

PACKAGE TEST WEIGHTS

Overall Pkg Tare Weight (PTW) + (98% Overflow Capacity (OFC) x # of Inner Pkg (# IP))					
PTW	+	(98% OFC)	x	# IP)	
1,875.0	+	2,380.5	x	6	Methanol/Water
1,875.0	+	2,522.6	x	6	Water
Methanol/Water:		16.1	kg	35.4	lb
Water:		17.0	kg	37.4	lb

AUTHORIZED PACKAGE GROSS MASS CALCULATION (APGM)

Overall Pkg Tare Weight (PTW) + (Product SG (PSG) x 98% Overflow (OFC) x # of Inner Pkg (# IP))						
PTW	+	(PSG	x	98% OFC	x	# IP)
1,875.0	+	1.9	x	2,522.6	x	6
		30.6	kg	67.4	lb	

DROP HEIGHT					
Calculation For Product Specific Gravities Exceeding 1.2					
Product Specific Gravity (PSG) x Packing Group Multiplication Factor (MF)					
PSG	x	MF	Packing Group: II		
1.9	x	1.00		<u>Required Drop Height</u>	<u>Actual Drop Height</u>
		1.90	Meter	74.8 Inches	75 Inches

STACKING TEST MINIMUM LOAD CALCULATIONS					
Number of Packages in a 3m High Stack (118.2 / Overall Pkg Height (OH) - 1)					
118.2 / Overall Height of one Pkg (OH) - 1					
<u>(118.2</u>	/	<u>OH)</u>	-1	=	<u># 3m HS</u>
118.2	/	13.50	-1	=	7.8
Stacking Test Load Calculation (Individual Package)					
Authorized Pkg Gross Mass (APGM) x # of Pkg in a 3m High Stack (# 3m HS)					
<u>APGM</u>	x	<u># 3m HS</u>			
30.6	x	7.8			
			238.7 kg	526.2 lb	